

Trip Consultancies BV
Brederodestraat 22
2406 XS Alphen a.d. Rijn
The Netherlands

Colour Fastness Testing BS EN ISO105-C10:2007

Sample Refs and Testing Conditions

Test	Method	Colour
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @30°C MODIFIED METHOD	2609 RED/B
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @60°C	2609 RED/B
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @30°C MODIFIED METHOD	2609 RED/NON
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @60°C	2609 RED/NON
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @30°C MODIFIED METHOD	2609 GREEN/B
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @60°C	2609 GREEN/B
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @30°C MODIFIED METHOD	2609 GREEN/NON
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @60°C	2609 GREEN/NON
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @30°C MODIFIED METHOD	2609 GREEN/B/PE
COLOUR FASTNESS TO WASHING	BS EN ISO 105-C10:2007 @60°C	2609 GREEN/B/PE

Please note the colour fastness washing @ 30°C fall outside of the scope of ISO 105-C10:2007.

Results

Colour Fastness to Washing - Method/Temp 30°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Red / B	4-5	4-5	4-5	4-5	4-5	5	5	N/A	N/A
Colour Fastness to Washing - Method/Temp 60°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Red / B	4-5	4-5	4-5	4	4-5	5	5	N/A	N/A
Colour Fastness to Washing - Method/Temp 30°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Red / Non	4-5	4-5	4-5	4	4-5	5	5	N/A	N/A
Colour Fastness to Washing - Method/Temp 60°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Red / Non	4-5	4-5	4 Whiter	4	4-5	4-5	4-5	N/A	N/A
Colour Fastness to Washing - Method/Temp 30°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Green / B	4-5	4-5	4-5	4-5	5	5	5	N/A	N/A

Results Continued

Colour Fastness to Washing - Method/Temp 60°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Green / B	4-5	4-5	4 Whiter	4-5	5	5	5	N/A	N/A
Colour Fastness to Washing - Method/Temp 30°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Green / Non	4-5	5	4-5	4-5	5	5	5	N/A	N/A
Colour Fastness to Washing - Method/Temp 60°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Green / Non	4-5	5	4 Whiter	4	5	5	5	N/A	N/A
Colour Fastness to Washing - Method/Temp 30°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Green / B / Pet	4-5	5	5	4	5	5	5	N/A	N/A
Colour Fastness to Washing - Method/Temp 60°C									
Sample		Staining (Multifibre DW) onto:						Requirements	
	Change	Acetate	Cotton	Nylon	Polyester	Acrylic	Wool	Change	Stain
2609 Green / B / Pet	4-5	5	5	4	5	5	5	N/A	N/A

Reporting scale (Grey Scale)

- 5 – No change of colour compared to control
- 1- Significant change of colour to control



Signed : Wendy Callaghan MSc MRSC

External Report Reference LEHTX00710489


End of report

PWC Solutions Ltd,
Stanlaw Abbey Business Centre,
Dover Drive,
Ellesmere Port Cheshire,
CH65 9BF

Laundry Testing

Nr. 2609Red/B

27-09-2013

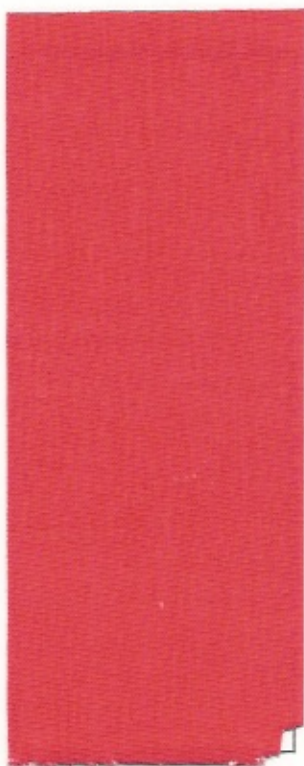

100% Cotton 43T B
Heat pressed at 160°C 60 sec.
TINK Red Laundry Test1, 30°C



100% Cotton 43T B
Heat pressed at 160°C 60 sec.
TINK Red Laundry Test4, 60°C



100% Cotton 43T B
Heat pressed at 160°C 60 sec.
TINK Red Original

PWC Solutions Ltd,
Stanlaw Abbey Business Centre,
Dover Drive,
Ellesmere Port Cheshire,
CH65 9BF

Laundry Testing

Nr. 2609Green/B

27-09-2013



100% Cotton 43T B
Heat pressed at 160°C 60 sec.
TINK Green Laundry Test1, 30°C



100% Cotton 43T B
Heat pressed at 160°C 60 sec.
TINK Green Laundry Test4, 60°C



100% Cotton 43T B
Heat pressed at 160°C 60 sec.
TINK Green Original

PWC Solutions Ltd,
Stanlaw Abbey Business Centre,
Dover Drive,
Ellesmere Port Cheshire,
CH65 9BF

Laundry Testing

Nr. 2609Red/Non

27-09-2013



100% Cotton 43T Non B
Heat pressed at 160°C 60 sec.
TINK Red Laundry Test1, 30°C



100% Cotton 43T Non B
Heat pressed at 160°C 60 sec.
TINK Red Laundry Test4, 60°C



100% Cotton 43T Non B
Heat pressed at 160°C 60 sec.
TINK Red Original

PWC Solutions Ltd,
Stanlaw Abbey Business Centre,
Dover Drive,
Ellesmere Port Cheshire,
CH65 9BF

Laundry Testing

Nr. 2609Green/Non

27-09-2013



100% Cotton 43T Non B
Heat pressed ar 160°C 60 sec.
TINK Green Laundry Test1, 30°C



100% Cotton 43T Non B
Heat pressed ar 160°C 60 sec.
TINK Green Laundry Test4, 60°C



100% Cotton 43T Non B
Heat pressed ar 160°C 60 sec.
TINK Green Original

PWC Solutions Ltd,
Stanlaw Abbey Business Centre,
Dover Drive,
Ellesmere Port Cheshire,
CH65 9BF

Laundry Testing

Nr. 2609Green/B/PET

27-09-2013



100% PET 43T B
Heat pressed at 160°C 60 sec.
TINK Green Laundry Test1, 30°C



100% PET 43T B
Heat pressed at 160°C 60 sec.
TINK Green Laundry Test4, 60°C



100% PET 43T B
Heat pressed at 160°C 60 sec.
TINK Green Original